



Advanced Materials Manufacturing & Characterization

journal home page: www.ijammc-griet.com



Multi Response Optimisation for Correlated Responses in EDM using Principal Component Analysis

Ritanjali Sethy¹, C.K. Biswas² and Shailesh Dewangan³

1-3Department of Mechanical Engineering, National Institute of Technology, Rourkela, India

ARTICLE INFO

Article history:

Received: 11-06-2013

Accepted: 29-07-2013

Keywords:

Electrical Discharge Machining (EDM),
AISI P20 tool steel,
PCA, PCA-based GRA..

ABSTRACT

This study presents a new method to determine multi-objective optimal condition using Principal Component Analysis (PCA) based on Grey Relational Analysis (GRA) Method for Characteristics as Material Removal Rate (MRR), Tool Wear Rate (TWR) and Surface Roughness (Ra) on Electrical Discharge Machining (EDM). In this paper, an attempt has been made to machining the AISI P20 tool steel by using cylindrical copper electrode perform on EDM. A well-designed L27 orthogonal array based on the Taguchi method were conducted on input parameters as current, pulse on time, up-time, working time and inter electrode gap.

and/or to optimize the process parameters.

Introduction

Electrical discharge machining process is one of the most successful, non-traditional machining processes for machining newly developed high strength alloys with high degree of dimensional accuracy, electrically conductive material irrespective of its hardness with economical cost of production. In Electrical Discharge Machining (EDM), it is important to select machining parameters for achieving optimal machining performance [1]. EDM is based on thermoelectric energy between the work piece and an electrode and it is one of the best alternatives for machining an ever increasing number of high-strength, non-corrosion, and wear resistant materials. EDM researchers have explored a number of ways to improve and optimize the MRR, TWR and SR like Dhar and Purohit [2] evaluates the effect of effect of MRR, TWR, SR with Process parameters taken in to consideration were the current, the pulse duration Al-4Cu-6Si alloy-10 wt. % SiCp composites. Despite a range of different approaches, all the research work in this area shares the same objectives of achieving more efficient material removal coupled with a reduction in tool wear and improved surface quality. Many researchers have carried out experimental research works using Taguchi method [3] with the aim to understand the effect of various process parameters on different response variables

Considerable researches have been carried out in recent time aiming to establish an objective method for solving multi-response optimization problems using Taguchi method. The goal of multi response optimization is to find out the settings of the input variables that can achieve an optimal compromise of the response variables. With this aim, several multi response optimization approaches, in this regard, usually found in engineering literature, are Weighted Signal-To-Noise (WSN) ratio method [4] and Multi Response Signal-To-Noise (MRSN) ratio method [5]. It has been shown that the grey-based Taguchi technique can optimise the multi-response processes because of grey relational analysis is used for solving the complicated inter relationships among the multiple responses [6]. In order to consider the possible correlation between the responses, some researchers have proposed to make use of PCA [7, 8].

Principal Component Analysis (PCA) is a multivariate technique for forming new uncorrelated variables through a linear composite of the original variables. The maximum number of new variables that can be formed is equal to the number of original variables. In this paper, principal component analysis PCA-based Grey relational analysis (GRA) approaches which can optimize multiple responses taking care of the possible correlations between the responses are applied to experimental data on the EDM processes. Tong and Wang [9] proposed the PCA-based GRA method. The main advantage of PCA is that once the patterns in data have been identified, the data can be compressed, i.e., by reducing the number of dimensions, without much loss of information.

- Corresponding author: Ritanjali Sethy
- E-mail address: ritanjali.sethy@gmail.com
- Doi: <http://dx.doi.org/10.11127/ijammc.2013.07.11>

II. EXPERIMENTAL DESIGN

The experiment was conducted on die-sinking EDM machine with 30 mm diameter of cylindrical copper tool electrode and EDM oil as dielectric. The work material was AISI P20 tool steel which is a semi-circular shaped work piece material (100 mm diameter and 10 mm thickness). Machining was carried out for 60 min for each experimental run. In this study, the effect of five process parameters, namely, current (Ip), on-time (Ton), up-time (Tup), work time (Tw), inter electrode gap (IEG) and some fixed parameters have taken like duty cycle (tau), voltage (V), flushing pressure (Fp) and polarity of the EDM process that shown in Table 1 was studied on three performance characteristics (responses) i.e., MRR, TWR, SR. The MRR is calculated as the ratio of the difference of weight of the work piece before and after machining to the machining time and density of the material. TWR is expressed as the ratio of the difference of weight of the tool before and after machining to the machining time and density of the material and the SR was measured with Talysurf (Model: Taylor Hobson, Surtronic 3+) with parameters cut-off length, Ln= 4 mm, Sample length, Lc=0.8 mm and filter=2CR ISO.

The experiment designed using Taguchi method, which is an optimisation methodology that uses an orthogonal array to study the entire parameter space with only a small number of experiments. Taguchi's signal-to-noise (S/N) ratios are logarithmic functions of desired output and serve as objective functions in the optimisation process. Usually, there are three categories of performance characteristics in the analysis of the S/N ratio. The S/N ratio (η_{ij}) for jth response variable corresponding to ith trial (i=1, 2, . . . , m; j=1, 2, . . . , p) can be computed using the following equations:

$$\text{Lower-The-Better (LTB),} \\ \eta_{ij} = -10 \times \log_{10} \left(\frac{1}{n} \sum_{k=1}^n y_{ijk}^2 \right) \quad (1)$$

$$\text{Higher-The-Better (HTB),} \\ \eta_{ij} = -10 \times \log_{10} \left(\frac{1}{n} \sum_{k=1}^n \frac{1}{y_{ijk}^2} \right) \quad (2)$$

$$\text{Nominal-The-Best (NTB),} \\ \eta_{ij} = 10 \times \log_{10} \left(\frac{\bar{y}_{ij}^2}{s_{ij}^2} \right) \quad (3)$$

Where, n=number of repeated experiments, y_{ijk} = experimental value of jth response variable in ith trial at kth replication. The number of experimental run =m and p is the number of responses. Basically, in this paper only two S/N ratios are used i.e., LTB for TWR and SR and HTB for MRR. The experimental layout of the S/N ratios for the three response variables with the final output are given in Table 4. The modelling is done by MINITAB16 software using L27 array with PCA method. After applying PCA on S/N ratios, the eigenvalues and the corresponding eigenvectors obtained are shown in Table 2.

III. PROPOSED OPTIMISATION (GRA Method):

GRA based on the grey system theory means that a system in which part of information is known and part of information is unknown i.e., from black through grey to white is

used for solving the complicated inter relationships among the multiple responses. GRA is a normalization evaluation technique is extended to solve the complicated multi-performance characteristics optimization effectively.

IV. PROCEDURE

The value obtained in the PCA-based GRA method is simply called overall quality performance index (OQPI).

Step 1. Compute the S/N ratio for each response.

Step 2. To obtain uncorrelated principal component scores (PCS), conduct PCA on the S/N ratios. The PCS value of lth component (l=1,2,...,p) corresponding to each trial by using Equation:

$$PCS_{il} = a_{l1}\eta_{i1} + a_{l2}\eta_{i2} + \dots + a_{lp}\eta_{ip} \quad (4)$$

The coefficients of the lth component, i.e., $a_{l1}, a_{l2}, \dots, a_{lp}$ are the elements of the eigenvector corresponding to the lth eigenvalue of the correlation matrix of the response variables.

Step 3. Since a larger PCS is always desired, normalized the principal component scores for lth principal component in ith trial (X_{il}) by using Equation:

$$X_{il} = \frac{PCS_{il} - PCS_{l}^{min}}{PCS_{l}^{max} - PCS_{l}^{min}} \quad (5)$$

Step 4. Based on normalised principal component scores, calculate the grey relational coefficient (γ_{il}) computed as follows:

$$\gamma_{il} = \frac{\Delta_l^{min} + \xi \times \Delta_l^{max}}{\Delta_{il} + \xi \times \Delta_l^{max}} \quad (6)$$

Where, $\Delta_{il} = |1 - X_{il}|$, $\Delta_l^{min} = \min\{\Delta_{l1}, \Delta_{l2}, \dots, \Delta_{lm}\}$, $\Delta_l^{max} = \max\{\Delta_{l1}, \Delta_{l2}, \dots, \Delta_{lm}\}$, ξ is the distinguishing coefficient which range varies from [0, 1] and usually, it is set to 0.5.

Step 5. The OQPI's values can be obtained using the following expression:

$$OQPI_i = \sum_{l=1}^p w_l \gamma_{il} \quad (7)$$

Where, $\sum_{l=1}^p w_l = 1$

Step 6: Use geometric average to calculate the factor effects based on OQPI values, and then decide the optimal factor-level combination based on the-higher-the-better factor effects.

The computed OQPI values corresponding to different trials for the PCA-based method are shown in Table 3 which gives the level averages of the control factors and the optimal machining conditions separately for this three responses are calculated by reduction of principal components which shown in Figure 1 and the values are given in Table 5. A confirmatory test is conducted with the optimal parameter setting and shown in Table 5.

TABLE 1. INPUT PARAMETERS WITH THEIR UNIT

Control Parameter					
Parameter	Symbol	Level			Unit
		1	2	3	
Discharge current	Ip	2	5	8	A
Pulse on Time	T _{on}	100	300	500	μs
Lift Time	T _{up}	0.0	0.7	1.4	s
Work time	T _w	0.2	0.6	1.0	s
Inter Electrode gap	IEG	90	70	250	μm
Fixed Parameter					

Duty Cycle	(ζ)	90	%
Voltage	V	45	V
Flashing Pressure	Fp	0.3	Kgf/cm ²

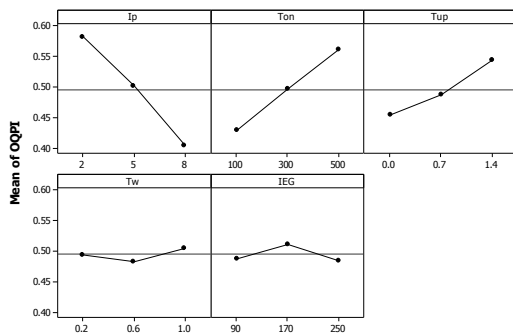


Figure 1: For OQPI

Principal Component	Eigen Value	Proportion of variation explained	Eigenvector
First	2.1798	0.727	[0.541, -0.580, 0.609]
Second	0.5291	0.176	[0.808, 0.558, -0.187]
Third	0.2911	0.097	[0.231, -0.594, -0.771]

TABLE 3. MEAN VALUES OF OQPI

Level	Ip	Ton	Tup	Tw	IEG
1	0.5808	0.4289	0.4538	0.4952	0.4876
2	0.5010	0.4955	0.4871	0.4835	0.5127
3	0.4031	0.5604	0.5439	0.5061	0.4845

V. CONCLUSION

GRA is a very useful tool for predicting optimization of the multi response problems and it does not involve complicated mathematical theory or computation. So, it can be employed by the engineers without a strong statistical background. The proposed procedure has been shown to be as successful in obtaining the optimal parameter conditions i.e. , Ip1 Ton3 Tup3 Tw3 IEG2 based on the-higher-the-better factor effects using GRA employing principal component analysis is most able to consistently obtain the optimal parameter design for correlated multiple quality characteristics.

REFERENCES

1. C. L. Lin, J. L. Lin and T. C. Ko, 2002, "Optimisation of the EDM Process Based on the Orthogonal Array with Fuzzy Logic and Grey Relational Analysis Method ", Int J Adv Manuf Technol, 19, pp. 271-277.
2. S. Dhar, R. Purohit, N. Saini, A.Sharma, and G.H. Kumar, 2007, "Mathematical modelling of electric discharge machining of cast Al-4Cu-6Si alloy-10 wt.% SiCP

3. M.S. Phadke, 1989, "Quality Engineering Using Robust Design", Prentice Hall: Englewood Cliffs, NJ.
4. C.Y. Tai, T.S. Chen, M.C Wu, 1992, "An enhanced Taguchi method for optimizing SMT processes", Journal of Electronics Manufacture, 2, pp. 91-100.
5. R. Ramakrishnan, L. Karunamoorthy, 2006, "Multi response optimization of wire EDM operations using robust design of experiments", International Journal of Advanced Manufacturing Technology, 29, pp. 105-112.
6. J. L. Lin and Y. S. Tarn, 1998, "Optimization of the multi-response process by the Taguchi method with grey relational analysis", Journal of Grey System, 10(4), pp. 355-370.
7. F.-C. Wu, C.C Chyu, 2004, "Optimization of correlated multiple quality characteristics robust design using principal component analysis", Journal of Manufacturing Systems, 23, pp. 134-143.
8. R. Chakravorty, S. K. Gauri, and S. Chakraborty, 2012, "Optimization of correlated responses of EDM process", Materials and Manufacturing Processes, 27, pp. 337-347.
9. L.I. Tong and C.H. Wang, 2002, "Multi-response optimization using principal component analysis and grey relational analysis", International of Industrial Engineering, 9, pp. 343-350.

TABLE 4. EXPERIMENTAL RESULTS WITH FINAL OUTPUT

Run	Ip	Ton	Tup	Tw	IEG	S/N MRR	S/N TWR	S/N SR	OQPI
1	1	1	1	1	1	5.5338	41.4116	-11.7542	0.5008
2	1	1	1	1	2	5.8624	36.5363	-11.5268	0.4594
3	1	1	1	1	3	5.4979	35.8635	-11.1261	0.4613
4	1	2	2	2	1	-4.4558	43.8764	-8.6914	0.6021
5	1	2	2	2	2	-3.5501	39.4939	-7.6403	0.5534
6	1	2	2	2	3	-3.8601	36.5363	-7.1587	0.5305
7	1	3	3	3	1	-9.8240	37.9239	-4.6090	0.6166
8	1	3	3	3	2	-10.9184	52.7654	-5.5751	0.8924
9	1	3	3	3	3	-9.4861	37.9239	-4.9595	0.6100
10	2	1	2	3	1	2.2789	35.8635	-13.3863	0.4649
11	2	1	2	3	2	4.1419	32.6157	-14.5671	0.4279
12	2	1	2	3	3	3.6254	30.5449	-14.1684	0.4219
13	2	2	3	1	1	-6.6884	39.4939	-13.5521	0.5321
14	2	2	3	1	2	-5.5720	40.3546	-13.7327	0.5534
15	2	2	3	1	3	-7.5661	37.3292	-15.3283	0.5668
16	2	3	1	2	1	9.3935	41.9382	-6.5222	0.5095
17	2	3	1	2	2	9.9566	37.1397	-7.9588	0.4605
18	2	3	1	2	3	8.2951	49.0691	-8.8809	0.5716
19	3	1	3	2	1	12.1470	28.8981	-17.0861	0.3813
20	3	1	3	2	2	11.3954	27.0133	-16.9515	0.3732
21	3	1	3	2	3	11.5188	26.4479	-17.6846	0.3692
22	3	2	1	3	1	19.7928	28.8499	-18.7303	0.3681
23	3	2	1	3	2	19.6519	30.5449	-18.2763	0.3793
24	3	2	1	3	3	19.9760	29.6297	-17.8974	0.3734
25	3	3	2	1	1	16.6461	34.8464	-17.5934	0.4126
26	3	3	2	1	2	16.1021	43.8764	-18.0292	0.5143
27	3	3	2	1	3	16.6615	39.4939	-18.4441	0.4557

TABLE 5 PREDICTED VALUES

Optimization Method	Optimal condition	Predicted S/N ratio			Confirmatory Test		
		MRR	TWR	SR	MRR	TWR	SR
GRA method	<i>Ip1 Ton3 Tup3 Tw3 IEG2</i>	-9.84	44.2	-5.1	-12.06	45.03	-6.3